

Preparation and Characterization of Microcrystalline Cellulose for Pharmaceutical Excipient: A Review

by Ririn Suharsanti

Submission date: 04-Jun-2025 07:45AM (UTC+0700)

Submission ID: 2691650694

File name: n2022_TJNPR_REVIEW_MCC_1_.pdf (414.87K)

Word count: 6095

Character count: 32755

Preparation and Characterization of Microcrystalline Cellulose for Pharmaceutical Excipient: A Review

Intan M. Cahyani^{1,2}, Endang Lukitaningsih⁴, Adhyatmika Adhyatmika³, Teuku N. S. Sulaiman^{3*}

¹ Doctoral Program of Pharmaceutical Science, Faculty of Pharmacy, Gadjah Mada University, Indonesia

² STIFAR "Yayasan Pharmasi", Letjend Sarwo Edie Wibowo KM 1, Semarang, Indonesia

³ Department of Pharmaceutics, Faculty of Pharmacy, Gadjah Mada University, Indonesia

⁴ Department of Pharmaceutical Chemistry, Faculty of Pharmacy, Gadjah Mada University, Indonesia

ARTICLE INFO

Article history:

Received 11 August 2022

Revised 29 August 2022

Accepted 19 October 2022

Published online 01 November 2022

Copyright: © 2022 Cahyani *et al.* This is an open access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

ABSTRACT

Microcrystalline cellulose (MCC) is widely used as an additive excipient in the pharmaceutical, cosmetic, and food industries. Previous studies have been conducted on the extraction of natural MCC from plant fibers, stem powder, seeds, husks, and organic waste. This review was aimed at discussing the preparation and characterization of MCC for pharmaceutical excipients. Google, Science Direct, PubMed, and Scopus search were conducted using specific keywords to find recent information published between 2010 and 2022. MCC is produced in four stages: delignification, bleaching, cellulose hydrolysis using a dilute acid solution while keeping reaction conditions in mind, and drying. Several analytical techniques have been developed to characterize MCC, including Fourier transform infrared, scanning electron microscopy, energy-dispersive X-ray spectrophotometry, and X-ray diffractometer to calculate the crystallinity index and predict the type of cellulose produced. The MCC from natural components yield 33.0 - 91.71% and crystallinity index was between 11 - 82.4%. The properties such as true, bulk, and tapped densities, as well as flow properties (Carr's index, angle of repose, Hausner index, and compressibility index) indicate that MCC from natural materials such as ground husk, corn stalks, ensete glaucum, wheat straw, water hyacinth, and sugarcane bagasse has the potential as tablet excipients when compared to the characteristics of commercial MCC. Therefore, they can be used as a reference for direct compression.

Keywords: Characterization, Delignification, Hydrolysis, Microcrystalline cellulose, Pharmaceutical excipient.

Introduction

Microcrystalline cellulose (MCC) is a tasteless and odorless white crystalline powder made up of porous particles. MCC is slightly soluble in a 5% w/v solution of sodium hydroxide (NaOH) but practically insoluble in water, acid solutions, and some organic solvents. It is relatively stable physically and chemically in ambient conditions, and it is normally stored in dry and cool environments.¹ MCC is an essential supplementary excipient in the pharmaceutical sector, particularly as a tablet excipient, in addition to being an ingredient in food and cosmetic products.² Microcrystalline cellulose preparation involves the hydrolysis of alpha-cellulose pulp with mineral acids. In recent years, research has been conducted to produce MCC from natural components such as plant fibers,³ stem powder, seeds, husks, and organic waste, including coffee husks,⁴ date seeds,⁵ ensete glaucum,⁶ giant reeds,⁷ rice straw and banana plant wastes.⁸ Furthermore, *Saccharum spontaneum* (Kans grass),⁹ tea wastes,¹⁰ parawood sawdust,¹¹ wheat straw,¹² water hyacinth,¹³ and sugarcane bagasse,¹⁴ have all been reported as ingredients for the synthesis of MCC. Both wood and non-wood sources can produce plant fibers, and both types of fibers have good biodegradability, renewability, low density, high strength, and high stiffness.¹⁵

*Corresponding author. E mail: tn_saifullah@ugm.ac.id
Tel: +6289501332718

Citation: Cahyani IM, Lukitaningsih E, Adhyatmika A, Sulaiman TNS. Preparation and Characterization of Microcrystalline Cellulose for Pharmaceutical Excipient: A Review. Trop J Nat Prod Res. 2022; 6(10):1570-1575. <http://www.doi.org/10.26538/tjnpr/v6i10.3>

Official Journal of Natural Product Research Group, Faculty of Pharmacy, University of Benin, Benin City, Nigeria.

Cellulose is a fibrous, tough, water-insoluble substance that is essential for maintaining the structure of natural fibers.¹⁶ The majority of wood and non-wood fibers are made of cellulose, which is present in natural sources in amounts equivalent to 1.5 x 10¹⁰ tons of the annual biomass production.¹¹ It is a linear homopolymer made up of homo monosaccharide macromolecules known as anhydroglucose that are connected by (1-4)-glycosidic bonds. It can be degraded by microbial and fungal enzymes. Amorphous and crystalline regions can be seen in the structure of cellulose.¹ Apart from cellulose and hemicellulose, the other major lignins are components of plant fiber. Hemicellulose consists of various types of cyclic saccharides, whereas lignin is an amorphous polymer consisting of aromatic units such as guaiacyl, syringyl, and phenylpropane.¹¹ The aim of the present review was to discuss the preparation and methods used for the characterization of MCC for pharmaceutical excipients.

Methods

For this review article, Google, Science Direct, PubMed, and Scopus search using keywords like "extraction," "isolation," "preparation," "characterization," "properties," "microcrystalline cellulose," and "pharmaceutical excipient" were used to find recent information. The content was limited to the preparation of natural MCC, the use of acid-base preparation methods, and characterization using predetermined tools. Only articles published between 2010 and 2022 were consulted.

Results and Discussions

Various sources of microcrystalline cellulose

Microcrystalline cellulose is a derivative product of pure cellulose with a crystal structure that is chemically derived from lignocellulosic biomass. Initially, wood and cotton were the primary sources of MCC,

but as technology advanced, lignocellulosic biomass, a type of non-wood biomass, became a popular alternative. MCC can be found in coffee husks,⁴ date seeds,⁵ ensete glaucum,⁶ giant reeds,⁷ rice straw, and banana plant wastes.⁸ *Saccharum spontaneum* (Kans grass),⁹ tea wastes,¹⁰ parawood sawdust,¹¹ wheat straw,¹² water hyacinth,¹³ sugarcane bagasse,¹⁴ groundnut husk,¹⁷ cornstalks,¹⁸ and betung bamboo.⁹ The MCC produced from various alternative sources exhibits characteristics that are acceptable by the standard, so the search for additional natural sources is currently being encouraged more and more. MCC has unique mechanical and physicochemical features, including renewability, biodegradability, non-toxicity, high mechanical properties, low density, large surface area, good biocompatibility, and hygroscopicity.¹⁵

Preparatory methods of microcrystalline cellulose

Microcrystalline cellulose is typically produced through the controlled hydrolysis of cellulose obtained as a pulp from fibrous plant materials in a diluted mineral acid solution. The hydro cellulose is filtered and then washed with water after hydrolysis. After that, a dry powder is created by spray-drying the aqueous slurry. Hydrolysis using mineral acids on various α -cellulose precursors is a simple method of MCC preparation to reduce the degree of polymerization.¹⁹ Alpha-cellulose itself is not available as a free form but is bound to lignin, which is called lignocellulose. For lignin to be released from the complex during hydrolysis, the lignocellulose must first undergo delignification. This process is important because lignin can inhibit acid penetration for hydrolysis to take place. The efficiency of the delignification process is influenced by heating time, solvent solution concentration, solvent-to-raw material ratio, temperature, and pressure. Heat mechanics, acid treatment, alkaline treatment, and treatment with organic solutions are all pretreatment options for lignocellulosic waste.

Conventional delignification can be done by hydrolyzing lignocellulosic materials using strong acids. However, this method is not as effective as the use of bases because of several drawbacks, which include low cooking yields, high production costs, low delignification rates, and environmental pollution from cooking solution waste. As shown in Figure 1, NaOH acts by breaking the lignin structure to release cellulose from its bonds. The hydroxyl ions (OH⁻) released from NaOH breaks the bonds from the basic structure of lignin while sodium ions (Na⁺) binds with lignin to form sodium phenolics that will dissolve easily to form a black-colored solution known as a black liquid.²⁰ In research conducted by Cheng *et al.*, it was established that the lignin and cellulose bonds could be broken more successfully during the delignification process by first treating the acid catalyst in the solvent. It was reported that the yield could be increased up to six times at 98.0%.²¹ As presented in Table 1, delignification processes using bases like NaOH are thus commonly employed in recent studies. All of them use NaOH solution with a concentration of 3 to 17.5% and a solid-to-solution ratio of 1:10 and 1:20 at 80-170°C over a range of 30 min to 14 h. It has been demonstrated that the release of lignin and hemicellulose is aided by a combination of physical structural damage, mechanical fragmentation, and chemical structure depolymerization by alkali treatment. Under these conditions, higher cellulose content and crystal transformation from cellulose I to II require a lower NaOH concentration. This process happens in wheat straw.²⁰ Bleaching is required to remove the black color from the solution. It can remove lignin and carbohydrates that are not completely separated from the pulp. The procedure involves submerging plant fiber in hydrogen peroxide (H₂O₂) or sodium hypochlorite (NaClO) solution, both of which are strong oxidizers that can degrade dye molecules by reacting with the oxygen they release. Free radicals created by hydrogen peroxide can be unstable and can interact with molecules of dye or other large, highly pigmented organic compounds.²² Microcrystalline celluloses can be prepared by the chemical method of acid hydrolysis, the biological method of enzymatic hydrolysis, and the mechanical method of steam explosion. Acid hydrolysis is reported to be the most efficient method because it is cheaper and faster.⁷ It involves the reaction of hydronium ion (H₃O⁺) with the amorphous form of cellulose, which causes the hydrolytic breakdown of the glycosidic bonds.¹⁵ The crystalline form of cellulose, however, cannot be affected by ions in the same way because it is more acid-resistant and thus

remains intact.²³ While using strong acids like hydrochloric acid (HCl),^{5,6,10,12} sulfuric acid (H₂SO₄),^{4,8,9} and combinations of acids such as HCl/ H₂SO₄/ nitric acid (HNO₃) will improve the hydrolysis efficiency, but it will not affect the properties of the MCC produced.⁷ According to studies, the amounts of cellulose produced from Rice straw and banana plant waste after alkaline-acid and acid-alkaline treatments, respectively, 41.3-52.5% and 43.6-48.5%, did not significantly differ.⁸ Similar to the delignification stage, it is important to pay attention to several factors, including acid concentration, time, reaction temperature, and the proportion of pulp to the acid solution during hydrolysis. Table 1 displays the results of the optimal hydrolysis conditions. Tea waste has an acid to ingredient ratio of 1:20, an HCl concentration of 1.5 mol/L, a processing time of 90 min, a temperature of 65°C, and an extraction yield of 86.7%.¹⁰ Meanwhile, for *Saccharum spontaneum* (Kans grass), the optimal processing conditions are 5% H₂SO₄, at a temperature of 50°C, with a pulp solution ratio of 1:15 for 120 min, with an MCC yield of 85%.⁹ Water hyacinth yield was 91.71% when processed optimally with 1.5 N HCl for 30 min,¹³ and sugarcane bagasse yield was 44.2% with 4% HNO₃ for 2 hr (1:8).¹⁴ In addition to acid hydrolysis, MCC from water hyacinth can also be prepared by enzymatic hydrolysis with properties resembling those of commercial MCC.²⁴ The final stage in the preparation of MCC is drying, which can be accomplished through air drying, oven drying, or freeze drying.

Characterization of microcrystalline cellulose

Many analytical techniques have been developed using Fourier transform infrared (FTIR), a sensitive, fast, and inexpensive infrared spectroscopy instrument to study polymers by measuring the absorption intensity and the wavelength of infrared (IR) radiation transformation. This has allowed a better understanding of the characteristics of natural MCC. Recently, Fourier infrared spectroscopy has been widely used to determine the chemical structure and functional groups of lignocellulose compounds.¹⁷ The results of an FTIR analysis are shown in Table 2. It demonstrates that while hemicellulose and lignin were expelled during chemical treatment, the MCC from the hydrolysis of all the materials studied retained its cellulose structure. These results also indicate that the use of different types of acids in the pulp hydrolysis process does not alter the chemical structure of cellulose. It implies that all MCC produced by the hydrolysis of various types of acids would exhibit FTIR spectra that were similar to those of Avicel PH 101 or commercial cellulose, which is the preferred form of cellulose for marketing.^{6,7,11,13} Information about the chemical composition and crystallographic structure of MCC can be identified using X-ray Diffraction (XRD) based on a solid crystal analysis of the atomic-scale structure of the material. X-rays have a wavelength equal to the distance between the atoms, which causes the diffraction of the crystalline solid.

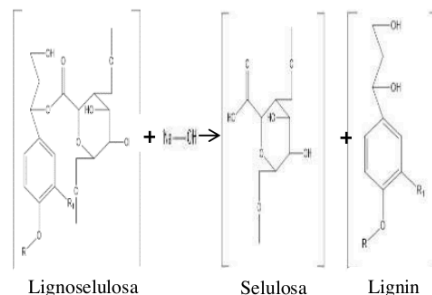


Figure 1: Mechanism of delignification with NaOH solution.

Table 1: Various preparation methods of microcrystalline cellulose

No	Raw Material	Preparation conditions			Yield (%)	Ref	
		Delignification	Bleaching	Hydrolysis			
1	Coffee husk	Solid : 4% NaOH (1:20) 3h	Solid : 1.7% NaClO (1:20) 4h	H ₂ SO ₄ 64% , 50°C, 40 min	Nd	61.8	4
2	Date Seeds	17.5% NaOH , 90°C, 3h	NaClO ₂ (≈10–15%) , 80°C, 45 min	Solid : 2.5 N HCl (1:11) 105 °C ± 2 °C, 45 min	freeze-dried	63	5
3	Ensete glaucum	NaOH	Sodium hypochlorite and hydrogen peroxide	2.5 M HCl , 105°C, 15 min	Nd.	33	6
4	Giant reed	NaOH (1.25M), room temperature 24h and 90°C 5h	Solid: 2.6 M H ₂ O ₂ and 4.4 M CH ₃ COOH solution (1:20) 5h Solid: 2.1 M H ₂ O ₂ and 1 M NaOH solution (1:20)	Solid : 2.5 M acid used single HCl, HNO ₃ , H ₂ SO ₄ , and the mixture (HCl / HNO ₃ (2: 1, v / v), HCl / H ₂ SO ₄ (2: 1, v / v)) (1:20) 100°C 30 min	Oven	34.5 (cellulose)	7
5	Rice straw and banana plant waste	Solid : 10% NaOH (1:10) 170°C, 2h	Solution equivalent to 60% sodium hypochlorite	Solid : 5% H ₂ SO ₄ (1:10) 170°C, 2h	air-dried.	41.3-52.5 (Alkaline-acid) 43.6-48.5(Acid-Alkaline)	8
6	Saccharum spontaneum	Solid : 3% NaOH (1:20) 14h	Hydrogen peroxide (H ₂ O ₂)	5-25% H ₂ SO ₄ within 2 - 8 hours temperature 50 - 120 Pulp: solution ratio (g / ml) 1:15 to 1:50. optimum of 5% H ₂ SO ₄ , at 50 ° C in 1:15 120 min.	oven	83	9
7	Tea waste	Solid : 10 mol/L NaOH (1:20) , 75°C, 4h	Solid : 5% NaClO solution (1:20) Solid : 0.45% H ₂ O ₂ solution (1:20)	0.5 - 1.5 mol/L HCl within 1 - 2 h , 65- 85 ° C material:solid ratio 1:15 to 1:25. optimum of 1.5 mol/L, HCl, at 65 ° C in 1:20 ,90 min.	vacuum - freezing	86.7	10
8	Parawood sawdust	Solid : 0.5M NaOH (1:10) 80°C 2h	Solid : 5% NaClO solution (1:10) room temperature, 2 h	Solid : 2 N HCl or H ₂ SO ₄ (1:10 and 1:15) 80°C, 2 and 4 h. optimum HCl 1:15,80°C 2h	oven	76.89-77.67 (cellulose)	11
9	Wheat Straw	Solid : 2% NaOH (1:20) 2 h	Solid : 0.7% NaClO solution (1:20) 1 h	H ₂ SO ₄ 65% 1h ; 2 h and HCl 2.5 N 1h then continue H ₂ SO ₄ 65% 1h ; 2 h	Freezin g-drying	Nd	12
10	Water Hyacinth	17.5% NaOH 80 ° C, 30 min	Solid : 3.5% NaClO solution (1:1) 100°C, 5 min	1-2 N HCl within 30-60 min , optimum of 1.5 N HCl 30 min	oven	91,71	13
11	Sugarcane Bagasse	NaOH 80 ° C, 1 h	15% H ₂ O ₂	HNO ₃ , H ₂ SO ₄ , and HCl (3%, 4%, 5%) 80° C, 2h optimum HNO ₃ 4% (1:8)	60° C, 24 h	44.20	14

Nd: Not detected

By measuring the height between the intensity of the crystal peak and the total intensity of the non-crystal peak, it is possible to determine the index crystallinity. The diffraction pattern under this condition exhibits many sharp points known as Bragg diffraction peaks. According to Table 2, the crystallinity index of MCC that came from different sources was between 50 - 82.4%. Using various MCC preparations, interesting results were produced on rice straw and banana plant waste, which produced different crystallinity indices of 60-66.7 (alkaline-acid) and 66-82.4% (acid-alkaline).⁸ The results of Type I and Type II cellulose are displayed in the identification of the type of cellulose.^{9,67,10,11} Based on the degree of purity, Type I and Type II cellulose are distinguished from one another. Type I cellulose, or α-cellulose, is long-chain cellulose, which is insoluble in 17.5% sodium hydroxide solution or strong alkaline solutions with a degree of polymerization of 600-1500. The function of α-cellulose is to determine the level of purity of the cellulose. The higher the α-cellulose content, the better the quality of the material. Type II cellulose, or β-cellulose, is short-chain cellulose, which can dissolve in a 17.5%

sodium hydroxide solution or a strong base with a degree of polymerization of 15-90 and can precipitate in neutral acidity.¹² Scanning electron microscopy (SEM) of micrographs revealed cellulose microcrystals from various materials having a rod-shaped and uniform structure similar to the reference MCC observed in the day-reported analysis.^{6,7,9,11} Zhao et al.,¹⁰ reported shorter results with some holes on the rough surface, while Ibrahim et al reported smoother results.⁸ However, it was also demonstrated that the effectiveness of each step in the preparation of the cellulose structure would affect its morphology. In date seeds, aggregation and irregular elongated or semi-spherical morphology were shown.⁵ The average particle size, according to the SEM results, was between 3.6 - 500 μm. Thermal properties are crucial in the characterization of bio-composites because a relatively high temperature is needed in the processing process. All of the materials in this discussion had good thermal stability, as determined by Thermogravimetric analysis (TGA) on MCC, which indicates that cellulose can be processed using acid hydrolysis to obtain a relatively high crystallinity index.¹⁹

Table 2: Characterization of microcrystalline cellulose

No	Raw Material	Characterization						Ref.
		FTIR	X-ray diffraction (XRD) Analysis		Scanning Electron Microscopy (SEM)	Particle Size (μm)	Thermogravimetric Analysis (TGC)	
			Cellulose type	Crystallinity Index (%)				
1	Coffee husk	Nd	Nd	50	fibres are arranged in parallel and an ordered assembly	60-500	good thermal stability	4
2	Date Seeds	Similar to cellulose	Cellulose type I	70	irregular and agglomerated elongated or semi-spherical morphology	100-300	enhanced thermal stability	5
3	Ensete glaucum	Similar to Avicel PH 101	Cellulose type I and II	53.41	elongated and rod-shaped structure	294.4	lower hygroscopicity than Avicel PH 101	6
4	Giant reed	Similar to Commercial MCC	Cellulose type I allomorph	73-80	micro-sized rod-like shape morphology dan non-uniform	7.79 - 8.52	thermal decomposition of MCC at a higher temperature compared to cellulose	7
5	Rice straw and banana plant waste	Similar to cellulose	Nd	60-66.7 (alkaline-acid) 66.7-82.4% (acid-alkaline)	smooth surface	3.6 - 7.6	there is a decrease in the degree of crystallinity	8
6	Saccharum spontaneum	Similar to cellulose	Nd	74.06	Rod-shape and uniformity structure	Nd	good thermal stability	9
7	Tea waste	Similar to cellulose	Cellulose type I	81	Rough surface with few holes and shorter fibers	Nd	good thermal stability	10
8	Parawood sawdust	Similar to Avicel PH 101	Cellulose type I	60	rod-like structure	30-100	higher thermal stability in the treatment using HCl compared to H ₂ SO ₄	11
9	Wheat Straw	Nd	Nd	Nd	Fiber-like particles like those obtained (single-step) and irregular-shaped particles with smooth surface (two-step)	5-65	Nd	12
10	Water Hyacinth	Similar to Avicel PH 101	Nd	78.23	Nd	Nd	Nd	13
11	Sugarcane Bagasse	Similar to cellulose	Nd	59.3	Nd	Nd	Nd	14

Nd: Not detected

Table 3: Properties of microcrystalline cellulose for pharmaceutical excipient

N0	Raw Material	Properties of Microcrystalline Cellulose								Ref
		pH	True density (g/mL)	Bulk density (g/mL)	Tapped density (g/mL)	Flow Properties			Moisture content (%)	
						Carr's index (%)	The Angle of repose (°)	Hausner index		
1	Groundnut Husk	6.4	1.47	0.26	0.38	Nd	44.23	1.47	Nd	17
2	Cornstalks	6	1.59	0.33	0.43	23.26	41	1.3	5.6	18
3	Ensete glaucum	5.3	1.48	0.33	0.56	40.11	49.01	1.65	5.75	6
4	Betung Bamboo	6.8	Nd	0.32	0.47	31	31.39	1.45	4.36	2
5	Wheat Straw	Nd	1.58-1.68	0.06-0.15	0.09-0.19	18.57-32.33	Nd	1.23-1.48	Nd	12
6	Water Hyacinth	7.3	0.36	0.52	Nd	30.91	20.69	1.44	3.22	13
7	Sugarcane Bagass	Nd	Nd	0.07	0.08	8.45	50.20	1.08	6.27	14

Nd: Not detected

Properties of microcrystalline cellulose for pharmaceutical excipient

Microcrystalline cellulose has a very wide range of applications in the pharmaceutical industry, especially in the formulation of solid dosage form.²⁵ When comparing MCC-filled tablets to those made with other diluents, researchers found that MCC-filled tablets had better qualities like hardness, low brittleness, quick disintegration time, and high drug release rate. Direct pressing in tableting is widely used as it provides a uniform particle size, does not require a granulation process, produces more stable tablets, and is economically profitable. However, not all excipients can be used for the direct compression technique. MCC is the material of choice for direct pressing tableting because of its excellent flow property.²⁶ Furthermore, MCC is also widely used in suspensions and dry syrups because it can reduce the rate of sedimentation of the solid particles. MCC is also co-processed with other excipients to be used as a direct-compressed tablet filler-binder, such as with Kollidon ®K30,²⁷ colloidal silicon dioxide,²⁸ lactose and StarCap 1500,²⁹ *Cedrela odorata* Gum, alginate acid³¹ and lactose-Kollidon ®K30.³² Numerous studies have been conducted to investigate the properties of MCC for pharmaceutical excipients, including pH, moisture content, density, and flow properties, which are critical benchmark parameters for the quality of MCC given its broad function in the pharmaceutical industry. Table 3 displays the properties of MCC for pharmaceutical excipient made from groundnut husk,¹⁷ cornstalks,¹⁸ *Ensete glaucum*,⁶ betung bamboo,² wheat straw,¹² water hyacinth,¹³ and sugarcane bagasse.¹⁵ The flow properties of MCC from acid hydrolysis were good based on the Carr's index, Angle of repose, and Hausner index, which are equivalent to commercial MCC, which is the standard marketed form. Therefore, MCC from plants can be developed as excipients in pharmaceutical preparations, especially for solid dosage forms such as tablets. The current raw materials for the pharmaceutical industry are active ingredients and excipient, which also play an important role in determining the quality of the preparations. There are numerous ways to make tablets, each of which has advantages and disadvantages. One of them is the direct compression method, which requires less time and lower cost to produce than other methods due to its formula and manufacturing process efficiency. One drawback of this method is that not all active ingredients can be directly compressed due to their poor flowability and compressibility. It is estimated that less than 20% of the active substance can be compressed directly into tablets. The remaining 80% are made up of active ingredients that flow poorly and compress poorly, making it impossible to directly compress tablets. This problem can be overcome by using the right additives and can be directly compressed to produce quality tablets, one of which is microcrystalline cellulose.³³ In tablet preparations, cellulose microcrystals are primarily used as a filler.²⁵ As a direct compression tablet excipient, its high affinity for cellulose microcrystals is a factor to be taken into account.³⁴ This is because the tablet surface has free hydroxyl groups, which improve the binding, adhesion, and film strength of the substance.³⁵ MCC is additionally utilized in tablet formulation as a lubricant.³⁶ The tableting ability of MCC decreases when used in conjunction with magnesium stearate in hand mixing.³⁷ MCC is a multifunctional excipient, and the concentration at which it is used in the formula determines how hard the final tablet will be without affecting how quickly the drug will be released.³⁸ The preparation method for MCC affects tablet strength as well, with aqueous solutions producing stronger tablets than hydroalcoholic solutions.³⁹ The cavity created by the arrangement of microcrystalline cellulose particles allows relatively high levels of water permeation into the 3D tablet, lengthening the time before disintegration.⁴⁰ Meanwhile, it functions as a standard tablet disintegrant with a swelling mechanism as a result of the tablet absorbing water.⁴¹ Due to their size falling under the category of microparticles, cellulose microcrystals can ensure uniformity of the dosage content and improve the dispersibility of paracetamol in tablets.⁴² The performance is even better if it is co-processed together with polyvinyl pyrrolidone (PVP), which exhibits excellent flowability, tablet ability, and low ejection force.⁴³ Although the co-processed with colloidal silicon dioxide results did not demonstrate an improvement in the tablet strength,⁴⁴ MCC is excellent for direct printing because it has many advantages over other tablet excipients. The efficient direct molding

method is the preferred method, which has encouraged many manufacturers of raw materials to produce cellulose microcrystals with various physical and chemical characteristics. The compressibility index, which is the most important factor, is described by the physical and morphological properties of MCC in the relationship between tablet application performance.⁴⁵

Conclusion

The steps in MCC preparation are delignification, bleaching, and hydrolysis. To optimize the quality, various strong acids, such as hydrochloric acid, sulfuric acid, or nitric acid, can be used for hydrolysis by varying the concentration, temperature, time, and ratio of the acid to pulp solution. The MCC yield was 33.0 to 91.71%. The characterization of the produced MCC revealed that it was comparable to commercial MCC, which is the standard marketed form. This indicates that the MCC may be developed as an excipient in pharmaceutical preparations, particularly for solid dosage forms like tablets. Carr's index was between 18.57 and 40.11%, the angle of repose ranged from 20.69 to 50.20°, and Hausner's index was between 1.08 and 1.65. Microcrystalline cellulose has several functions in tablet formulations, including as a diluent, filler-binder, disintegrant, and lubricant, making it very effective for direct compression.

Conflict of Interest

The authors declare no conflict of interest.

Authors' Declaration

The authors hereby declare that the work presented in this article is original and that any liability for claims relating to the content of this article will be borne by them.

Acknowledgements

Financial support from The Indonesian Education Scholarship Program (BPI) within the Indonesian Ministry of Education and Culture (Kemendikbud RI) funded by the Indonesian Endowment Fund for Education/Lemba Pengelola Dana Pendidikan (LPDP).

References

- Sheskey PJ, Cook WG, Cable CG, editors. Handbook of Pharmaceutical Excipients. Eighth. Washington DC: Pharmaceutical Press.2017; 1216p.
- Kharismi RRAY, Sutriyo, Suryadi H. Preparation and characterization of microcrystalline cellulose produced from betung bamboo (*dendrocalamus asper*) through acid hydrolysis. J Young Pharm. 2018; 2:79–83.
- Xie J, Hse CY, De Hoop CF, Hu T, Qi J, Shupe TF. Isolation and characterization of cellulose nanofibers from bamboo using microwave liquefaction combined with chemical treatment and ultrasonication. Carbohydr Polym. 2016; 151:725–34.
- Collazo-Bigliardi S, Ortega-Toro R, Chiralt Boix A. Isolation and characterization of microcrystalline cellulose and cellulose nanocrystals from coffee husk and comparative study with rice husk. Carbohydr Polym. 2018; 191:205–15.
- Abu-Thabit NY, Judeh AA, Hakeem AS, Ul-Hamid A, Umar Y, Ahmad A. Isolation and characterization of microcrystalline cellulose from date seeds (*Phoenix dactylifera* L.). Int J Biol Macromol. 2020; 155:730–9.
- Pachauu L, Dutta RS, Hauzel L, Devi TB, Deka D. Evaluation of novel microcrystalline cellulose from *Ensete glaucum* (Roxb.) Cheesman biomass as sustainable drug delivery biomaterial. Carbohydr Polym. 2019; 206:336–43.
- Tarchoun AF, Trache D, Klapötke TM, Derradji M, Bessa W. Ecofriendly isolation and characterization of microcrystalline cellulose from giant reed using various acidic media. Cellulose. 2019; 26(13–14):7635–51.
- Ibrahim MM, El-Zawawy WK, Jüttke Y, Koschella A, Heinze T.

- Cellulose and microcrystalline cellulose from rice straw and banana plant waste: Preparation and characterization. *Cellulose*. 2013; 20(5):2403–16.
9. Baruah J, Deka RC, Kalita E. Greener production of microcrystalline cellulose (MCC) from *Saccharum spontaneum* (Kans grass): Statistical optimization. *Int J Biol Macromol*. 2020; 154:672–682.
 10. Zhao T, Chen Z, Lin X, Ren Z, Li B, Zhang Y. Preparation and characterization of microcrystalline cellulose (MCC) from tea waste. *Carbohydr Polym*. 2018; 184:164–70.
 11. Chuayplod P and Aht-Ong D. A study of microcrystalline cellulose prepared from parawood (*Hevea brasiliensis*) sawdust waste using different acid types. *J Met Mater Miner*. 2018; 28(2):106–14.
 12. Krivokapić J, Ivanović J, Djuriš J, Medarević D, Potpara Z, Maksimović Z, Ibrić S. Tableting properties of microcrystalline cellulose obtained from wheat straw measured with a single punch bench top tablet press. *Saudi Pharm J*. 2020; 28(6):710–8.
 13. Fitriya F, Fithri NA, Wijaya DP, Sembiring EP. Optimization of acid concentration and hydrolysis time in the isolation of microcrystalline cellulose from water hyacinth (*Eichornia crassipes* solm). *Trop J Nat Prod Res*. 2021; 5(3):503–508.
 14. Fauziah B, Yuwono M, Isaeni, Nahdhia N, Sholihah F. Isolation and characterization of sugarcane (*Saccharum officinarum* L.) bagasse cellulose hydrolyzed with acid variation. *Trop J Nat Prod Res*. 2020; 6(6):856–62.
 15. Trache D, Hussin MH, Hui Chun CT, Sabar S, Fazita MRN, Taiwo OFA, Hassan TM, Haafiz MKM. Microcrystalline cellulose: Isolation, characterization and bio-composites application—A review. *Int J Biol Macromol*. 2016; 93:789–804.
 16. Rahman WA, Razak SF, Majid NA. Extraction and Characterization of Cellulose from Jackfruit Rind (*Artocarpus Heterophyllus*). *Sci Lett*. 2019; 13(1):1–7.
 17. Ohwoavworhua F, Adalakun T, Okhamafe A. Processing pharmaceutical grade microcrystalline cellulose from groundnut husk: Extraction methods and characterization. *Int J Green Pharm*. 2009; 3(2):97–104.
 18. Azubuike CP, Silva BO, Okhamafe AO. Pharmacopoeial and physicochemical properties of α -cellulose and microcrystalline cellulose powders derived from cornstalks. *Int J Green Pharm*. 2012; 6(3):193–8.
 19. Mohamad Haafiz MK, Eichhorn SJ, Hassan A, Jawaid M. Isolation and characterization of microcrystalline cellulose from oil palm biomass residue. *Carbohydr Polym*. 2013; 93(2):628–34.
 20. Gao C, Yang J, Zhang H, Xiao W, Han L. Quantitative and qualitative characterization of dual scale mechanical enhancement on cellulosic and crystalline-structural variation of NaOH treated wheat straw. *Bioresour Technol*. 2020; 312:123535.
 21. Cheng F, Zhao X, Hu Y. Lignocellulosic biomass delignification using aqueous alcohol solutions with the catalysis of acidic ionic liquids: A comparison study of solvents. *Bioresour Technol*. 2018; 249:969–75.
 22. Nugroho JJ. In office bleaching pada kasus diskolorasi ekstrinsik. *Mks Dent J*. 2014; 3(2):1–4.
 23. Ilyas RA, Sapuan SM, Ishak MR. Isolation and characterization of nanocrystalline cellulose from sugar palm fibres (*Arenga pinnata*). *Carbohydr Polym*. 2018; 181:1038–51.
 24. Suryadi H, Sutriyo, Angeline M, Murti MW. Characterization of Microcrystalline Cellulose Obtained from Enzymatic Hydrolysis of Alpha-Cellulose and its Application. *J Young Pharm*. 2018; 10(2):87–92.
 25. Thoerens G, Krier F, Rozet E, Carlin B, Evrard B. Understanding the impact of microcrystalline cellulose physicochemical properties on tabletability. *Int J Pharm*. 2015; 490(1–2):47–54.
 26. Zhao H, Zhao L, Lin X, Shen L. An update on microcrystalline cellulose in direct compression: Functionality, critical material attributes, and co-processed excipients. *Carbohydr Polym*. 2022; 278:118968.
 27. Syukri Y, Romdhonah R, Fazzri AN, Sholehuddin RF, Kusuma AP. Formulation of Chlorpheniramine Maleate Tablets Using Co-Processed Excipient As A Filler And Binder. *J Pharm Sci Community*. 2019; 16(1):29–35.
 28. Tonar M, Sinha AR, Singh AK. Process and Development of Co-Processed Excipient Silicified Microcrystalline Cellulose and Manufacture Paracetamol Tablet by Direct Compression. *Int J Pharm Sci Rev Res*. 2017; 42(1):191–6.
 29. Chauhan SI, Nathwani SV, Soniwala MM, Chavda JR. Development and Characterization of Multifunctional Directly Compressible Co-processed Excipient by Spray Drying Method. *AAPS PharmSciTech*. 2017; 18(4):1293–301.
 30. Adetunji OA and Odeniyi MA. Material and Compression Properties of Cedrela odorata Gum Co-Processed with Plantain Starch and Microcrystalline Cellulose. *Polim Med*. 2016; 46(1):35–43.
 31. Benabbas R, Sanchez-Ballester NM, Bataille B, Sharkawi T, Soulaïrol I. Development and pharmaceutical performance of a novel co-processed excipient of alginic acid and microcrystalline cellulose. *Powder Technol*. 2021; 378:576–84.
 32. Kusuma AP, Syukri Y, Sholehuddin RF, Fazzri AN, Romdhonah, Hakim BF. Optimization of Microcrystalline Cellulose PH 101, Lactose, and Kollidon® K 30 To Obtain Co-Processed Excipient Through Spray Drying. *Int J Drug Deliv Tech*. 2017; 7(2):83–8.
 33. Sulaiman TNS and Sulaiman S. Review: Eksipien Untuk Pembuatan Tablet Dengan Metode Kempa Langsung. *J Pharm Sci*. 2020; 3(2):64–76.
 34. Thoerens G, Krier F, Leclercq B, Carlin B, Evrard B. Microcrystalline cellulose, a direct compression binder in a quality by design environment - A review. *Int J Pharm*. 2014; 473(1–2):64–72.
 35. Sun CC. Mechanism of moisture induced variations in true density and compaction properties of microcrystalline cellulose. *Int J Pharm*. 2008; 346(1–2):93–101.
 36. Ali J, Saigal N, Baboota S, Ahuja A. Microcrystalline Cellulose as a Versatile Excipient in Drug Research. *J Young Pharm*. 2009; 1(1):6–12.
 37. Dun J, Chen H, Sun CC. Profound tabletability deterioration of microcrystalline cellulose by magnesium stearate. *Int J Pharm*. 2020; 590:119927.
 38. Abushammala H, Hashaikh R, Cooney C. Microcrystalline cellulose powder tableting via networked cellulose-based gel material. *Powder Technol*. 2012; 217:16–20.
 39. Tank D, Karan K, Gajera BY, Dave RH. Investigate the effect of solvents on wet granulation of microcrystalline cellulose using hydroxypropyl methylcellulose as a binder and evaluation of rheological and thermal characteristics of granules. *Saudi Pharm J*. 2018; 26(4):593–602.
 40. Yin X, Maharjan A, Fang L, Wu L, Zhang L, Shakya S, Qin W, Regmi B, York P, Sun H, Zhang J. Cavities spatial distribution confined by microcrystalline cellulose particles determines tablet disintegration patterns. *Powder Technol*. 2018; 339:717–27.
 41. Yassin S, Goodwin DJ, Anderson A, Sibik J, Wilson DI, Gladden LF, Zeitler JA. The Disintegration Process in Microcrystalline Cellulose Based Tablets, Part I: Influence of Temperature, Porosity and Superdisintegrants. *J Pharm Sci*. 2015; 104(10):3440–50.
 42. Nakamura S, Nakagawa M, Tanaka C, Yuasa H, Sakamoto T. Utility of microcrystalline cellulose to prevent drug segregation in direct powder compression. *J Drug Deliv Sci Technol*. 2019; 52:386–92.
 43. Sun WJ, Sun CC. A microcrystalline cellulose based drug-composite formulation strategy for developing low dose drug tablets. *Int J Pharm*. 2020; 585:119517.
 44. Van Veen B, Bolhuis GK, Wu YS, Zuurman K, Frijlink HW. Compaction mechanism and tablet strength of unlubricated and lubricated (silicified) microcrystalline cellulose. *Eur J Pharm Biopharm*. 2005; 59(1):133–8.
 45. Li J, Wang Z, Xiu H, Zhao X, Ma F, Liu L, Yi C, Zhang M, Kozliak E, Ji Y. Correlation between the powder characteristics and particle morphology of microcrystalline cellulose (MCC) and its tablet application performance. *Powder Technol*. 2022; 399:117194.

Preparation and Characterization of Microcrystalline Cellulose for Pharmaceutical Excipient: A Review

ORIGINALITY REPORT

10 %	7 %	4 %	7 %
SIMILARITY INDEX	INTERNET SOURCES	PUBLICATIONS	STUDENT PAPERS

PRIMARY SOURCES

1	Submitted to University of Mosul Student Paper	2 %
2	Submitted to Universitas Airlangga Student Paper	1 %
3	Submitted to The Robert Gordon University Student Paper	1 %
4	ir.unilag.edu.ng Internet Source	1 %
5	digitalknowledge.cput.ac.za Internet Source	1 %
6	www.sciencetechindonesia.com Internet Source	1 %
7	Submitted to Konsorsium Perguruan Tinggi Swasta Indonesia Student Paper	1 %
8	umpir.ump.edu.my Internet Source	1 %
9	Herman Suryadi, Jessica J. Judono, Merianda R. Putri, Alma D. Eclessia, Jiihan M. Ulhaq, Dinar N. Agustina, Triyani Sumiati. "Biodelignification of lignocellulose using ligninolytic enzymes from white-rot fungi", Heliyon, 2022 Publication	1 %
10	elibrary.tsri.or.th Internet Source	1 %

11 Philip Builders, Chris Alalor, John Avbunudiogba, Isreal Justice. "Survey on the Pharmaceutical Quality of Herbal Medicines Sold in Nigeria", Journal of Applied Pharmaceutical Science, 2015

Publication

1%

12 link.springer.com

Internet Source

1%

Exclude quotes On

Exclude matches < 1%

Exclude bibliography On